

Silicon-Based Photonic Integration Beyond the Telecommunication Wavelength Range

Gunther Roelkens, Utsav D. Dave, Alban Gassenq, Nannicha Hattasan, Chen Hu, Bart Kuyken, Francois Leo, Aditya Malik, Muhammad Muneeb, Eva Ryckeboer, Dorian Sanchez, Sarah Uvin, Ruijun Wang, Zeger Hens, Roel Baets, Yosuke Shimura, Federica Gencarelli, Benjamin Vincent, Roger Loo, Joris Van Campenhout, Laurent Cerutti, Jean-Baptiste Rodriguez, Eric Tournié, Xia Chen, Milos Nedeljkovic, Goran Mashanovich, Li Shen, Noel Healy, Anna C. Peacock, Xiaoping Liu, Richard Osgood, *Fellow, IEEE*, and William M. J. Green, *Senior Member, IEEE*

(Invited Paper)

Abstract—In this paper we discuss silicon-based photonic integrated circuit technology for applications beyond the telecommunication wavelength range. Silicon-on-insulator and germanium-on-silicon passive waveguide circuits are described, as well as the integration of III–V semiconductors, IV–VI colloidal nanoparticles and GeSn alloys on these circuits for increasing the functionality. The strong nonlinearity of silicon combined with the low nonlinear absorption in the mid-infrared is exploited to generate picosecond pulse based supercontinuum sources, optical parametric oscillators and wavelength translators connecting the telecommunication wavelength range and the mid-infrared.

Index Terms—Heterogeneous integration, mid-infrared, nonlinear optics, silicon photonics.

I. INTRODUCTION

SILICON photonics is attracting a lot of attention for optical interconnect applications in the datacenter [1]. This is mainly driven by the compactness of the integrated optical components and the fact that these devices can be fabricated using the mature CMOS fabrication infrastructure, resulting in high yield and high volume fabrication. In recent years, the scope of applications for silicon photonics has broadened to e.g. the area of bio-sensing [2] and bio-medical instrumentation [3], which are potentially also high volume markets. In these devices one typically holds on to the telecommunication wavelength range for their implementation. A particular class of sensing applications would however benefit from the availability of photonic integrated circuit technology in other wavelength ranges, while still being able to fabricate these devices in a CMOS environment. This has happened recently for visible wavelength applications, using SiN as the waveguide material [4]. This enables applications such as Raman and fluorescence spectroscopy. On the long-wavelength side of the telecommunication window photonic integrated circuit technology could be of particular interest for mid-infrared spectroscopic sensing systems that need to be portable and low-cost [5]. These systems, which probe the very specific and strong mid-infrared absorption spectrum of molecules in a gas, liquid or solid, are currently implemented using bulky and expensive equipment, preventing their widespread deployment. This is in stark contrast with the wide range of applications that could benefit from such a technology, ranging from the field of environmental sensing (e.g., air and water quality monitoring), life sciences (e.g., exhaled breath analysis and high throughput histopathology) to industrial process control and security. Besides spectroscopy, these waveguide circuits can find applications in emerging fields such as astrophotonics [6] or provide the toolset for next-generation optical communication systems operating in the 2- μm wavelength range [7]. This work discusses the first steps in the direction of silicon-based photonic integrated circuits for the short-wave infrared (up to

Manuscript received October 1, 2013; revised November 28, 2013; accepted November 28, 2013. This work was supported in part by the European Research Council project MIRACLE, the Flemish IWT-SBO project GlucoSens and the FWO-project NanoMIR.

G. Roelkens, U. D. Dave, A. Gassenq, N. Hattasan, C. Hu, B. Kuyken, F. Leo, A. Malik, M. Muneeb, E. Ryckeboer, D. Sanchez, S. Uvin, R. Wang, Z. Hens, and R. Baets are with the Photonics Research Group – Center for nano- and biophotonics (NB-Photonics), Sint-Pietersnieuwstraat 41, B-9000 Gent, Belgium (e-mail: gunther.roelkens@intec.ugent.be; utsavdeepak.dave@ugent.be; albangassenq@yahoo.fr; nannicha.hattasan@intec.ugent.be; chenhu@intec.ugent.be; bart.kuyken@intec.ugent.be; francois.leo@intec.ugent.be; amalik@intec.ugent.be; muhammad.muneeb@intec.ugent.be; eva.ryckeboer@intec.ugent.be; dsanchez@intec.ugent.be; sarah.uvin@ugent.be; rwang@intec.ugent.be; zeger.hens@ugent.be; roel.baets@intec.ugent.be).

Y. Shimura, F. Gencarelli, B. Vincent, R. Loo, and J. Van Campenhout are with the IMEC, B-3001 Leuven, Belgium (e-mail: shimura@imec.be; gencarel@imec.be; vincent@imec.be; loo@imec.be; joris.vancampenhout@imec.be).

L. Cerutti, J.-B. Rodriguez, E. Tournié are with the Institut d'Electronique, F-UMR 5214, Université Montpellier 2–CNRS, Montpellier, France (e-mail: cerutti@univ-montp2.fr; rodriguez@ies.univ-montp2.fr; Eric.Tournie@univ-montp2.fr).

X. Chen, M. Nedeljkovic, G. Mashanovich, L. Shen, N. Healy, and A. C. Peacock are with the Optoelectronics Research Centre, Faculty of Physical Sciences and Engineering, University of Southampton, Southampton, SO17 1 BJ, U.K. (e-mail: xc1y11@ecs.soton.ac.uk; M.Nedeljkovic@soton.ac.uk; g.mashanovich@soton.ac.uk; lishen@soton.ac.uk; noelhealy@soton.ac.uk; acp@orc.soton.ac.uk).

X. Liu and R. Osgood are with the Department of Electrical Engineering, Columbia University, New York, NY 10027 USA (e-mail: xpliu.columbia@gmail.com; rosgood@columbia.edu).

W. M. J. Green is with the IBM T. J. Watson Research Center, Yorktown Heights, New York, NY 10598 USA (e-mail: wgreen@us.ibm.com).

Color versions of one or more of the figures in this paper are available online at <http://ieeexplore.ieee.org>.

Digital Object Identifier 10.1109/JSTQE.2013.2294460

a wavelength of $2.5\ \mu\text{m}$) and the mid-infrared, in order to fill this gap. In this paper we will discuss the realization of integrated millimeter-scale spectrometers operating in the $2\text{--}5.5\ \mu\text{m}$ wavelength range, as well as the integration of other materials on the silicon waveguide platform (III–V semiconductors, IV–VI colloidal quantum dots and GeSn alloys) to extend the functionality with integrated lasers and photodetectors. Finally, we will discuss the potential of nonlinear optics on this waveguide platform, either to generate coherent mid-infrared radiation over a broad wavelength range or to translate mid-infrared radiation to the telecommunication wavelength window, where very well developed optical components are available.

II. SILICON-BASED PASSIVE WAVEGUIDE CIRCUITS FOR THE MID-INFRARED

Silicon-on-insulator has become a standard material platform for the integration of photonic devices in the telecommunication wavelength window. Well-developed processes are available including high quality waveguide definition, germanium epitaxy etc. Therefore we have explored the use of this material platform for operation at longer wavelengths, using the standard silicon photonics technology that is used today in multi-project wafer approaches. These waveguide structures consist of a 220 or 400-nm thick silicon waveguide layer on a $2\text{-}\mu\text{m}$ thick buried oxide layer on a silicon substrate. Using this technology very low waveguide losses ($\sim 0.5\ \text{dB/cm}$) in the $2\text{--}2.5\text{-}\mu\text{m}$ wavelength range have been obtained [8]. Similarly, on the 400 nm silicon waveguide platform 3-dB/cm waveguide losses at a wavelength of $3.8\ \mu\text{m}$ were obtained [9]. Besides low-loss waveguides, functional components for spectroscopic sensing systems were also demonstrated [10], including planar concave grating spectrometers and arrayed waveguide gratings in the $2\text{--}2.5\ \mu\text{m}$ [11] and $3.8\text{-}\mu\text{m}$ wavelength range [9]. The transmission spectrum of a silicon-on-insulator wavemeter (a wavelength demultiplexer circuit where the output channels intentionally overlap in order to accurately measure the wavelength of a laser line injected into the spectrometer through centroid detection) based on an arrayed waveguide grating is shown in Fig. 1(a). This device is implemented on the 220-nm silicon waveguide platform and measures $525\ \mu\text{m}$ by $775\ \mu\text{m}$. Fig. 1(b) shows the transmission spectrum of a planar concave grating spectrometer operating at $3.8\ \mu\text{m}$ implemented on the 400-nm silicon waveguide platform [12].

While silicon-on-insulator waveguide circuits are ideal for long-wavelength photonic integrated circuits operating in the 2 to $4\text{-}\mu\text{m}$ wavelength range, the SiO_2 buried oxide layer starts absorbing heavily beyond that wavelength. Also the leakage to the silicon substrate through the standard $2\text{-}\mu\text{m}$ thick SiO_2 layer becomes an issue. Therefore alternative silicon-based waveguide platforms need to be considered for operation beyond $4\text{-}\mu\text{m}$ wavelength. Several options are being explored, including free-standing silicon [13], [14] and air-clad silicon pedestal structures [15], [16] (which however limits the type of components that can be implemented since it is for example very difficult to make the free propagation region of a planar concave grating free-standing/on a pedestal), silicon-on-sapphire [17]–[21],

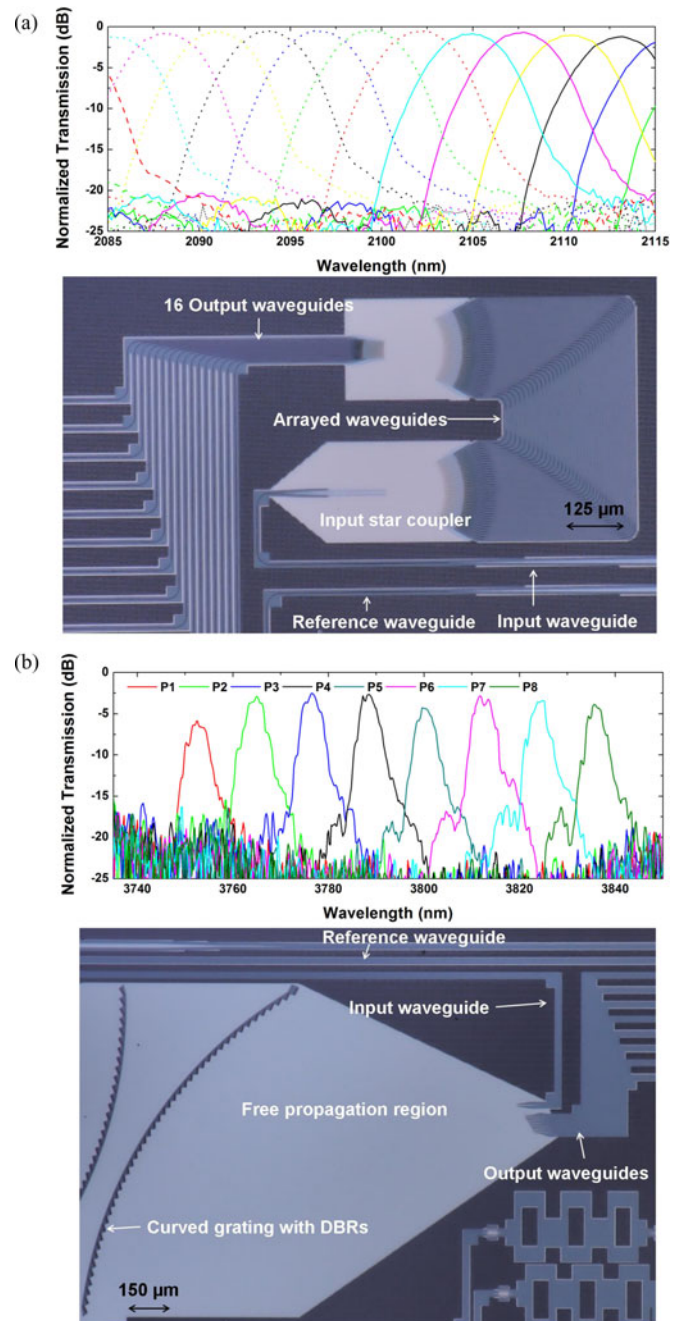


Fig. 1. (a) Normalized transmission spectrum and microscope picture of an integrated wavemeter operating in the $2\text{--}2.5\ \mu\text{m}$ wavelength range; (b) normalized transmission spectrum and microscope picture of a planar concave grating operating at $3.8\ \mu\text{m}$.

silicon-on-siliconnitride (which involves wafer bonding) [22] and SiN waveguide circuits [23]. The waveguide platform that we have adopted is germanium-on-silicon [24], since the epitaxial growth of germanium on a silicon wafer is well mastered and the processing of the germanium waveguide layer can be done in a CMOS fab. Germanium-on-silicon waveguides with waveguide losses of 3 dB/cm in the 5 to $5.5\text{-}\mu\text{m}$ wavelength range have been demonstrated (using a $2.2\text{-}\mu\text{m}$ wide and $2\text{-}\mu\text{m}$ thick germanium waveguide core on a silicon substrate) [25].

Given the wide transparency range of germanium from 2 to 14 μm , this platform should be able to handle most mid-infrared spectroscopic sensing applications. The lower index contrast between germanium and silicon compared to the silicon-on-insulator waveguide platform makes devices less compact however. Nevertheless, high performance arrayed waveguide grating spectrometers and planar concave grating spectrometers were recently realized as illustrated in Fig. 2 [25], [26].

III. EXTENDING THE FUNCTIONALITY OF LONG-WAVELENGTH PHOTONIC INTEGRATION PLATFORMS

In order to really make photonic integration a promising technology for spectroscopic sensing applications, the functionality of the passive waveguide platform needs to be extended with integrated photodetectors and laser sources. Different material systems can be used for this purpose. In this section we elaborate on the integration of GaSb-based photodetectors and lasers, and on the integration of PbS and HgTe colloidal nanoparticles and monolithically integrated GeSn for photodetection on the silicon-on-insulator waveguide platform. All these devices operate in the short-wave infrared (2–2.5- μm wavelength range) since photodetection at longer wavelengths typically requires thermo-electrically or cryogenically cooled devices for high performance operation. Integrating these on a silicon photonic IC would require cooling the whole IC which prevents the interaction between the liquid, gas or solid with the light to take place on the chip (due to condensation, freezing). In cases where photodetection at longer wavelengths is required, either off-chip cooled sources are envisioned or the use of nonlinear optics based wavelength translators can be considered, as will be discussed in Section IV.

A first approach to realize integrated photodetectors and lasers on a silicon chip is based on the epitaxial layer transfer of a GaSb-based compound semiconductor layer stack to the silicon waveguide circuit by means of die-to-wafer bonding. This process is well developed for InP-based epitaxy for operation in the telecommunication window [27] and has been ported to transfer GaSb-based epitaxy as well. In our work we use an adhesive bonding approach based on DVS-BCB, which is forgiving in terms of silicon and III-V wafer quality (surface roughness and contamination). The absorption spectrum of DVS-BCB is shown in Fig. 3(a), showing reasonably low absorption losses in the 1.5–3- μm wavelength range. The photodetector/laser process flow is shown in Fig. 3(b). For the photodetector integration, the epitaxial layer stack consists of a 500-nm thick InGaAsSb absorption layer (cut-off wavelength 2.5 μm) surrounded by p- and n-doped GaSb cladding layers. Both evanescently coupled and grating-assisted photodetectors have been demonstrated with responsivities up to 1.4 A/W at 2.3- μm wavelength [28]. The scalability of the heterogeneous integration of such photodetectors is illustrated in Fig. 4, showing the realization of a spectroscopic sensing system with 46 channels, covering the 1.5 to 2.3- μm wavelength range [11].

While GaSb-based detector integration provides the highest quality photodetectors for the 2 to 4- μm wavelength range, the cost of such devices can be quite high, due to the complex

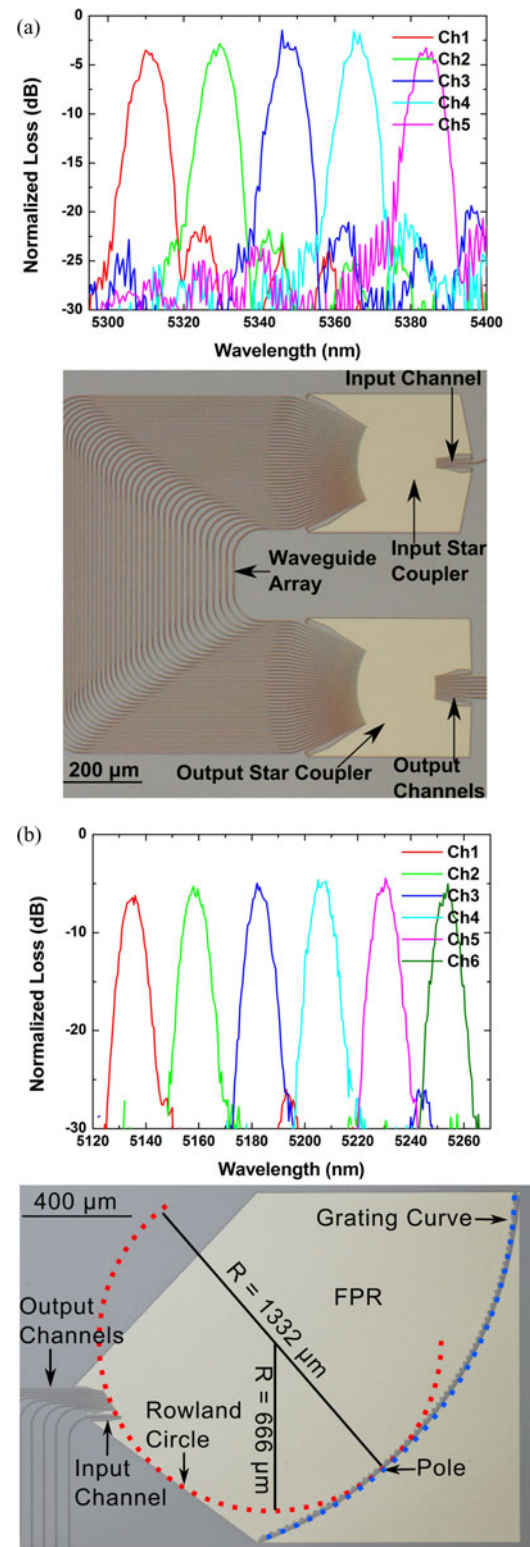


Fig. 2. (a) Normalized transmission spectrum of a germanium-on-silicon arrayed waveguide grating spectrometer operating in the 5–5.5 μm wavelength range and a microscope picture of the fabricated device; (b) normalized transmission spectrum of a germanium-on-silicon planar concave grating and a microscope picture of the fabricated device.

epitaxial growth required. Therefore, alternative solutions have been explored, namely the monolithic integration of GeSn layers on silicon as well as the integration of PbS/HgTe colloidal

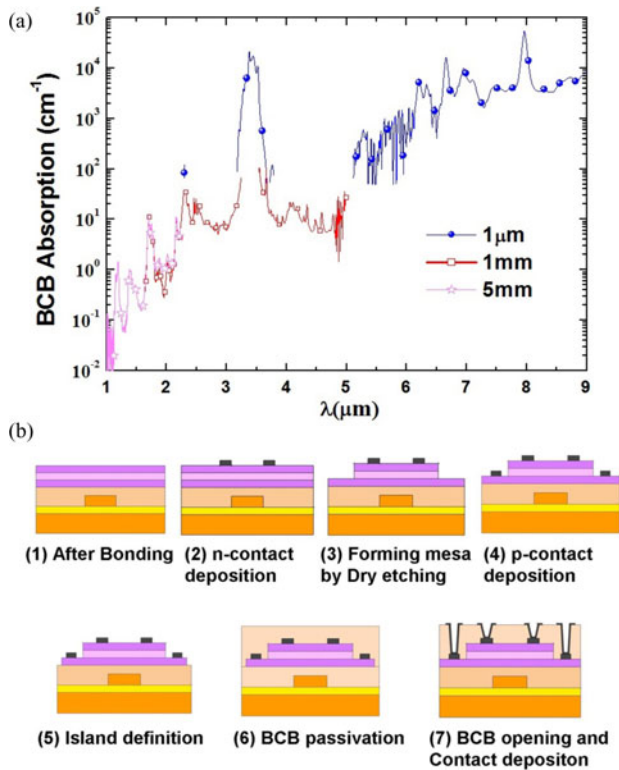


Fig. 3. (a) DVS-BCB absorption spectrum in the mid-infrared wavelength range; (b) InGaAsSb/GaSb photodetector/laser integration on silicon process flow.

nanoparticles for cost-sensitive (but perhaps less demanding) spectroscopy applications.

The use of GeSn epitaxy is inspired by the fact that the indirect (and direct) bandgap of germanium reduces when adding tin to the matrix [29]. This allows extending the cut-off wavelength of germanium detectors to the short-wave infrared ($\sim 2.5 \mu\text{m}$). Fig. 5(a) shows the photoresponse of a $\text{Ge}_{0.91}\text{Sn}_{0.09}$ multi-quantum well photoconductor structure as a function of the number of GeSn quantum wells [30]. Clearly, an extension of the cut-off wavelength compared to pure germanium detectors can be observed. These structures were grown on a germanium on silicon virtual substrate immediately providing a path to co-integrate these GeSn photodetectors with germanium-on-silicon waveguide structures, which have a propagation loss of 5 to 2 dB/cm in the 2.0 to 2.6- μm wavelength range as shown in Fig. 5(b).

An alternative approach relies on the integration of IV-VI semiconductors such as PbS, PbSe or Hg(Cd)Te on silicon waveguide circuits. Given the narrow bandgap of these materials, mid-infrared photodetectors can be realized. Current commercially available devices are based on epitaxial growth of these materials making it again an expensive technology. Therefore we developed a wet chemical synthesis method to grow PbS and HgTe nanoparticles in solution. These nanoparticles (ranging from 2–10 nm in size) can be deposited on silicon waveguide circuits in various ways, including spin-coating, drop-casting or inkjet-printing. Especially this last method is of great interest since it allows the efficient use of the nanomaterials. While

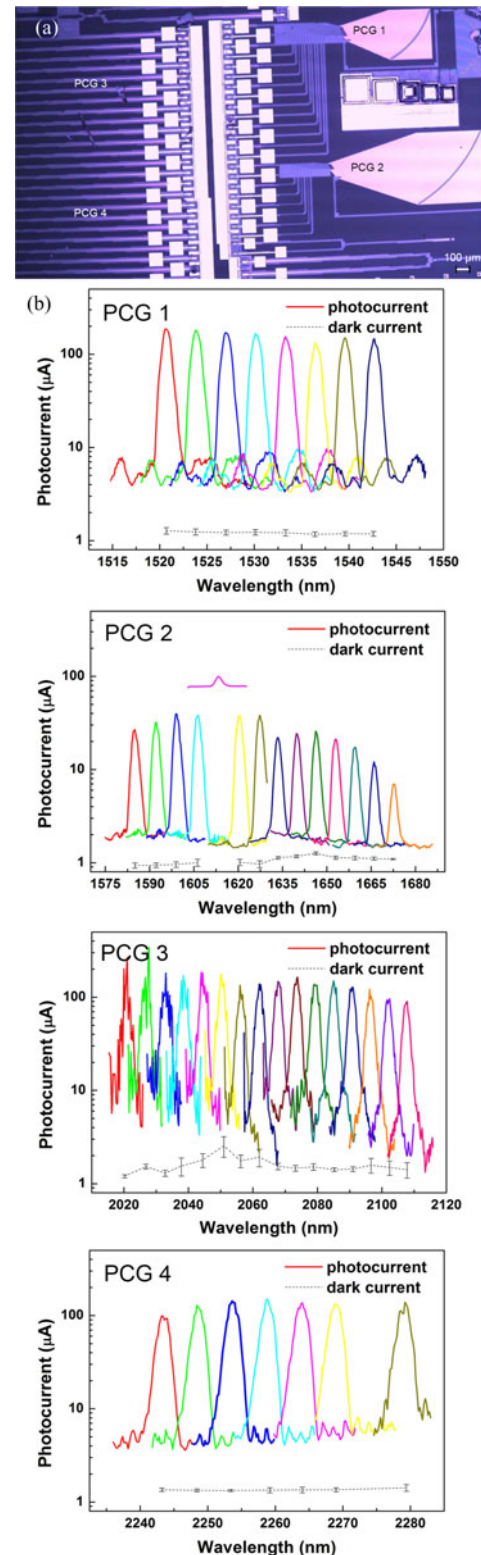


Fig. 4. (a) Microscope picture of the 46 channel integrated spectrometer covering the 1.5–2.3- μm wavelength range; (b) photocurrent versus wavelength for the various channels. The dark current at room temperature of the detectors is also indicated.

nanoparticle layers can easily be deposited to form integrated photoconductors or photodiodes, the organic ligands at the surface of the dots (which are required to prevent clustering of the

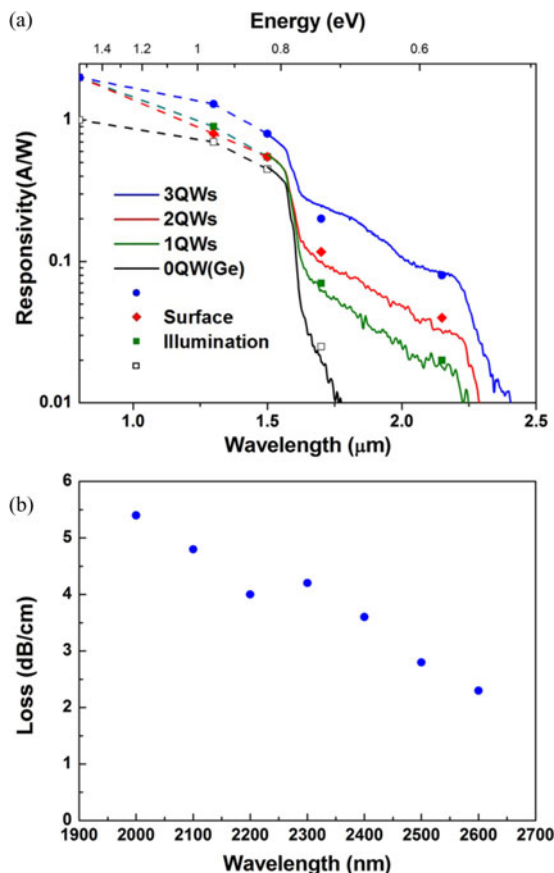


Fig. 5. (a) GeSn/Ge photoconductor integrated on a 200-mm silicon wafer demonstrating the potential of GeSn heterostructures for the realization of short-wave infrared optoelectronic devices on silicon photonic integrated circuits: responsivity as a function of wavelength and as a function of the number of GeSn quantum wells; (b) waveguide loss of germanium-on-silicon waveguides in the 2.0 to 2.6- μm wavelength range.

dots in a solution) prevents efficient carrier transport through such a layer [31]. In order to mitigate this problem, a wet chemical ligand exchange procedure was developed in which the long (~ 2 nm) organic ligands are replaced by very short inorganic ones (OH^- and S^{2-}). This ligand replacement is done in a layer by layer fashion in order to prevent the formation of cracks in the nanoparticle film due to the compaction of the film after ligand exchange. Organic ligand free films with good surface morphology have been realized as can be seen in Fig. 6, showing the Fourier Transform InfraRed (FTIR) spectrum of a nanoparticle film before and after ligand exchange and a scanning electron microscope image (SEM) of the realized film [32]. Based on this film deposition technology, surface illuminated photoconductors were realized as shown in Fig. 6(c), showing operation up to 2.4 μm and a high responsivity due to an internal gain mechanism typical of photoconductors which is related to the long carrier lifetime in the quantum dot film. This is attributed to trapping of photogenerated holes in nanoparticle surface states. Using HgTe nanoparticle films photodetection up to 2.8 μm has been demonstrated in our work, while others have shown the potential of this material system to go to the 5- μm wavelength range [33]. The integration of these nanoparticle films

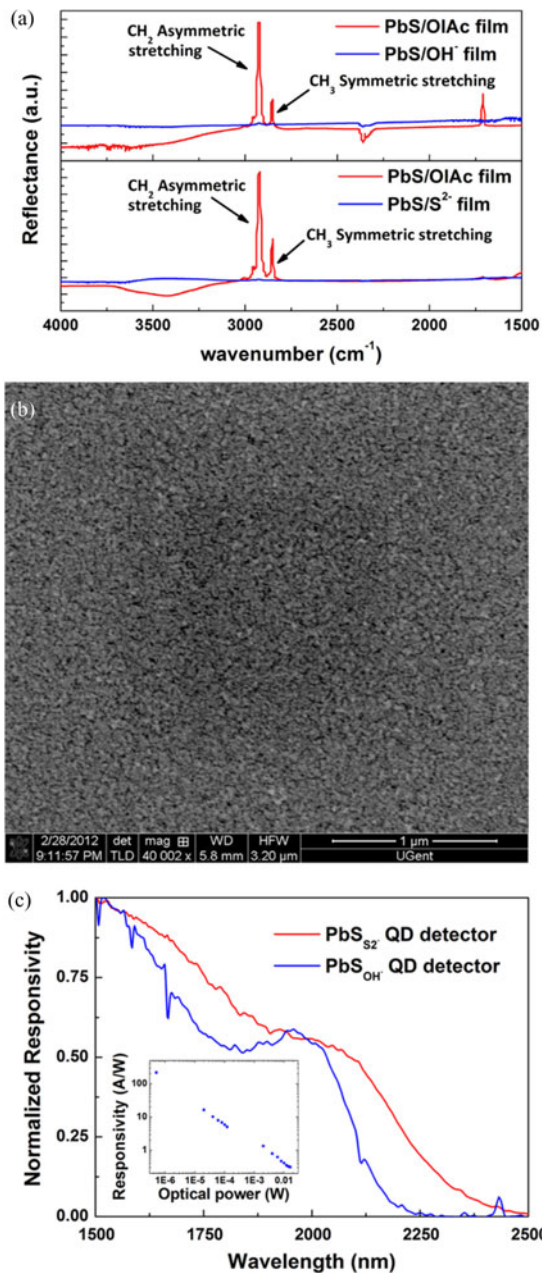


Fig. 6. (a) FTIR absorption spectrum of a colloidal nanoparticle film before ligand exchange and after ligand exchange—the peaks observed in the spectrum indicate absorption from C-H bonds coming from the oleic acid (OIAC) ligands, which are absent after ligand exchange; (b) SEM picture illustrating the good surface morphology based on the developed layer deposition technique; (c) responsivity and spectral response characteristics of a PbS colloidal quantum dot based photoconductor.

on silicon-on-insulator waveguide circuits is currently being developed.

While integrated photodetectors are of paramount importance for advanced integrated spectroscopic sensing systems, the availability of integrated laser sources operating in the short-wave or mid-infrared enable many more applications. While interband-cascade laser and quantum cascade lasers dominate the wavelength range beyond 3 μm , in the 2–3- μm wavelength range GaSb-based band-to-band semiconductor diode lasers

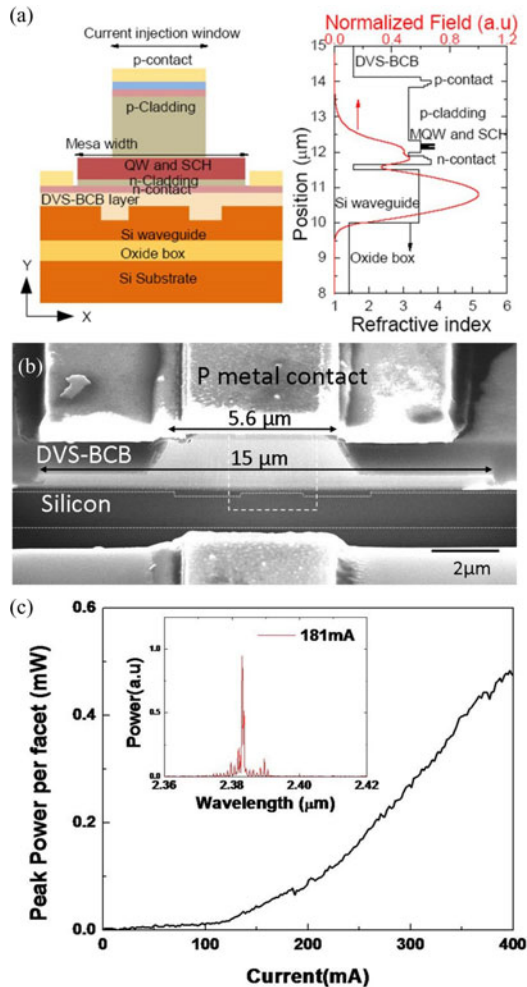


Fig. 7. (a) Schematic of the hybrid GaSb on silicon laser and the device mode profile; (b) SEM cross-section of the fabricated device; (c) light-versus-current and spectral characteristic of the fabricated Fabry-Perot laser cavity.

provide excellent performance. As an integration process for GaSb-epitaxy on silicon waveguide circuits is available and since several III-V on silicon laser designs were developed for the telecommunication wavelength range (using InP-based epitaxy) these device concepts can be ported to the GaSb on silicon platform. Fig. 7 illustrates a first generation Fabry-Perot GaSb-on-silicon hybrid laser using adhesive wafer bonding operating at 2.38- μm wavelength. The device is designed for high optical confinement in the silicon waveguide layer as illustrated in Fig. 7(a). The silicon waveguide layer thickness was therefore increased to 1.5 μm . A device cross-section is shown in Fig. 7(b), while the light-current characteristic of the device (pulsed operation at 10 $^{\circ}\text{C}$) is shown in Fig. 7(c). While these are still preliminary results it shows the potential of the GaSb on silicon waveguide platform. Another encouraging evolution is that recently GaSb on Si lasers have been realized based on hetero-epitaxial growth [34].

While in-plane emitting lasers allow for a straightforward interfacing to the silicon waveguide circuit, lower power consumption surface emitting devices operating in the 2–2.5- μm wavelength range are also of great interest. GaSb-based verti-

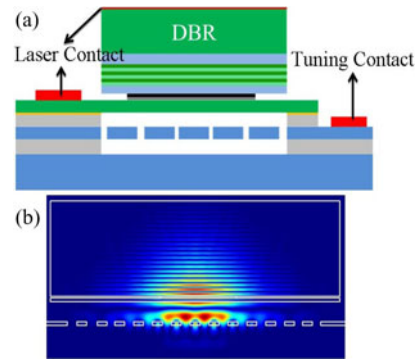


Fig. 8. (a) Schematic of the widely tunable GaSb/silicon hybrid VCSEL structure based on a high contrast grating as a bottom mirror. (b) Field profile of the resonant mode of the structure.

cal cavity surface emitting lasers (VCSELs) provide a solution here [35], [36]. However, the epitaxial growth of such structures is far from trivial given the very thick distributed Bragg reflector mirrors that are required. The high refractive index contrast available on the silicon waveguide platform can alleviate this issue. High contrast grating structures can be designed that provide very high reflectivity (>99.9%) over a broad wavelength range [37]. Using such high contrast gratings, hybrid VCSEL structures can be designed in which one DBR mirror is replaced by a high contrast grating, which – when made free standing – can be actuated in order to change the resonance wavelength of the cavity. The design of the grating can be adapted in such a way as to promote surface emitting operation or to promote coupling to the silicon waveguide layer. The device cross-section is illustrated in Fig. 8(a). In order to achieve operation around 2.3- μm wavelength, the grating structure was designed to have a period of 1.52 μm , a duty cycle of 50% and a silicon waveguide layer thickness of 220 nm. The field profile of the cavity mode (electrical field orientation along the grating lines) with a quality factor of 1600 is shown in Fig. 8(b). An analysis of the tuning behavior for this type of VCSEL (by electrostatic actuation of the high contrast grating) results in a wavelength tuning of 0.2 nm per 1 nm of grating displacement [38], allowing the realization of a widely tunable laser source.

IV. SILICON NONLINEAR OPTICS IN THE MID-IR

While the integration of III-V semiconductors on silicon waveguide circuits allows the generation and detection of mid-infrared light, the wavelength range of operation of a single III-V epitaxy is quite limited. Also, inherently detector performance decreases when moving to longer wavelengths. Nonlinear optics on a silicon waveguide platform can provide a solution to this problem. Silicon-on-insulator is a very attractive material platform for nonlinear optics, given the high refractive index contrast available and the high intrinsic Kerr nonlinearity of silicon. Especially in the short-wave infrared wavelength range silicon becomes an excellent material for nonlinear optics due to the absence of parasitic two-photon absorption [39]. Based on these properties several new device functionalities were demonstrated on the 220-nm silicon waveguide platform

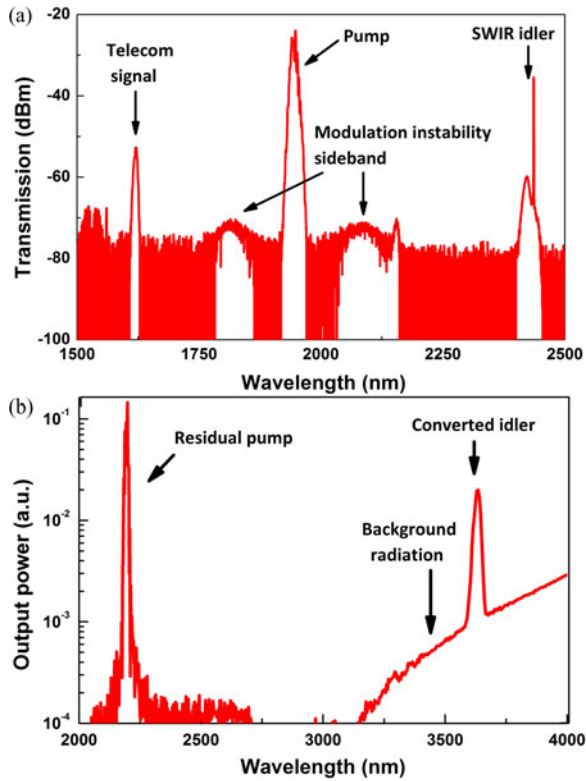


Fig. 9. (a) Wavelength translation over 800 nm using four-wave mixing in a 220 nm by 900-nm wide waveguide (pump: ps-pulse source operating at 1946 nm); (b) wavelength translation to the mid-infrared using a telecom-band tunable laser and a ps-pulse source operating at 2190 nm.

such as 1.5 to 2.5- μm supercontinuum generation using a 2120-nm wavelength picosecond pulsed laser source in crystalline silicon waveguides [40] or a similar bandwidth supercontinuum source using a 1950-nm picosecond thulium-doped fiber laser in hydrogenated amorphous silicon waveguides [41]. Also, given the very high parametric gain (>60 dB) that can be realized in a 2-cm long silicon waveguide, a fiber loop-based synchronously pumped optical parametric oscillator was demonstrated that was tunable from 2045 to 2125 nm [42]. As silicon high index contrast waveguides provide ample opportunity for dispersion engineering, the wavelength bands for which efficient four wave-mixing is achievable can be widely tuned. Of special interest is the phase matching of wavelength bands far away from the pump since this allows connecting the mid-infrared wavelength range to the telecommunication wavelength range. This might have different applications such as the generation of mid-infrared light based on the mixing of a telecom-band tunable laser and a short-wave infrared pump or the upconversion of mid-infrared light to the telecommunication band, which allows the detection of the mid-infrared signal using high performance uncooled detectors. This wavelength translation between the telecommunication band and the mid-infrared is illustrated in Fig. 9. Fig. 9(a) shows the up and down conversion over 800 nm using four-wave mixing in a 220-nm thick and 900-nm wide silicon waveguide [43], while Fig. 9(b) illustrates the same downconversion process to the 3.6- μm wavelength

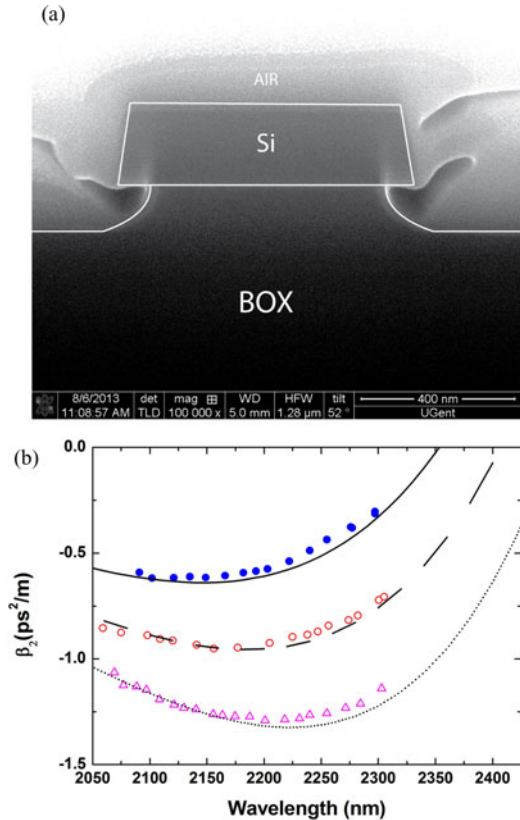


Fig. 10. (a) SEM cross-section of the undercut silicon waveguide for pushing the zero dispersion wavelength further into the infrared; (b) simulated and measured group velocity dispersion characteristic as a function of waveguide undercut (0-nm undercut, 55-nm undercut, 113-nm undercut).

range using a 400-nm thick and 1650-nm wide silicon waveguide [44].

Using standard 220-nm thick silicon waveguides, the only degree of freedom to engineer the waveguide dispersion of a silicon photonic wire in a standard CMOS fabrication flow is the width of the silicon waveguide. This limits the range over which the waveguide dispersion can be tuned. This issue can be tackled by, e.g., depositing dielectric layers on top of the waveguides (through chemical vapour deposition or atomic layer deposition [45]). However, such an approach does not allow tuning the anomalous dispersion regime to longer wavelengths, which is essential, since many nonlinear processes (broadband parametric amplification, solitonic propagation, . . .) rely on anomalous group velocity dispersion waveguides and longer wavelength operation is beneficial due to the reduced nonlinear losses. In order to accommodate this, undercutting of the silicon waveguide structures was used to push the anomalous dispersion region (and the associated zero dispersion wavelength) further in the infrared. Using buffered HF the undercutting can be very well controlled and as such, also the dispersion. This is illustrated in Fig. 10, showing the SEM cross-section of an undercut waveguide and the simulated and measured (according to the method described in [46]) second order dispersion characteristic of such a waveguide as a function of waveguide undercut. The waveguide loss increases from 0.6 to 0.9 dB/cm after undercutting, which is acceptable for the envisioned applications.

V. CONCLUSION AND PROSPECTS

Silicon photonics is an enabling technology for the realization of photonic integrated circuits since it leverages the mature CMOS technology for the realization of such components. While mainly developed for telecommunication wavelength range applications, it provides an excellent platform for applications both in the visible/near-infrared as in the mid-infrared. The silicon-on-insulator and germanium-on-silicon platform are ideally suited for the mid-infrared wavelength range, providing ample opportunity for novel and compact devices and systems operating in the mid-infrared. A tantalizing prospect is the realization of complete lab-on-a-chip spectroscopic sensing systems that can be based on various techniques such as absorption spectroscopy, photothermal [47] and photoacoustic [48] spectroscopy. Also, the co-integration of 'novel' materials such as graphene [49] and mid-infrared plasmonics [50] can spark the further development of next-generation integrated sensing systems.

REFERENCES

- [1] C. Gunn, "CMOS photonics for high-speed interconnects," *IEEE Proc. Comput. Sci.*, vol. 26, no. 2, pp. 58–66, Mar./Apr. 2006.
- [2] K. De Vos, J. Molera, T. Claes, Y. De Koninck, S. Popelka, E. Schacht, R. Baets, and P. Bienstman, "Multiplexed antibody detection with an array of silicon-on-insulator microring resonators," *IEEE Photon. J.*, vol. 1, no. 4, pp. 225–235, Oct. 2009.
- [3] Y. Li and R. Baets, "Homodyne laser doppler vibrometer on silicon-on-insulator with integrated 90 degree optical hybrids," *Opt. Exp.*, vol. 21, no. 11, pp. 13342–13350, 2013.
- [4] A. Subramanian, S. Selvaraja, P. Verheyen, A. Dhakal, K. Komorowska, and R. Baets, "Near infrared grating couplers for silicon nitride photonic wires," *IEEE Photon. Technol. Lett.*, vol. 24, no. 19, pp. 1700–1703, Oct. 2012.
- [5] J. G. Crowder, S. D. Smith, A. Vass, and J. Keddie, "Infrared methods for gas detection," in *Mid-infrared Semiconductor Optoelectronics*. New York, NY, USA: Springer-Verlag, 2006.
- [6] J. Bland-Hawthorn and P. Kern, "Astrophotonics: A new era for astronomical instruments," *Opt. Exp.*, vol. 17, no. 3, pp. 1880–1884, 2009.
- [7] N. MacSuihbne, Z. Li, B. Baeuerle, J. Zhao, J. Wooller, S. Alam, F. Poletti, M. Petrovich, A. Heidt, I. Giles, D. Giles, B. Palsdottir, J. Gruner-Nielsen, R. Phelan, J. O'Carroll, B. Kelly, D. Murphy, A. Ellis, D. Richardson, and F. Garcia Gunning, "Wavelength division multiplexing at 2 μm ," in *Proc. Eur. Conf. Opt. Commun.*, 2012, PDP Th3A3.
- [8] N. Hattasan, B. Kuyken, F. Leo, E. Ryckeboer, D. Vermeulen, and G. Roelkens, "High-efficiency SOI fiber-to-chip grating couplers and low-loss waveguides for the short-wave infrared," *IEEE Photon. Technol. Lett.*, vol. 24, no. 17, pp. 1536–1538, Sep. 2012.
- [9] M. Muneeb, X. Chen, P. Verheyen, G. Lepage, S. Pathak, E. Ryckeboer, A. Malik, B. Kuyken, M. Nedeljkovic, J. Van Campenhout, G. Mashanovich, and G. Roelkens, "Demonstration of silicon on insulator mid-infrared spectrometers operating at 3.8 μm ," *Opt. Exp.*, vol. 21, no. 10, pp. 11659–11669, 2013.
- [10] M. Nedeljkovic, A. Khokhar, Y. Hu, X. Chen, J. Soler Penades, S. Stankovic, H. Chong, D. Thomson, F. Gardes, G. Reed, and G. Mashanovich, "Silicon photonic devices and platforms for the mid-infrared," *Opt. Mater. Exp.*, vol. 3, no. 9, pp. 1205–1214, 2013.
- [11] E. Ryckeboer, A. Gassenq, M. Muneeb, N. Hattasan, S. Pathak, L. Cerutti, J.-B. Rodriguez, E. Tournie, W. Bogaerts, R. Baets, and G. Roelkens, "Silicon-on-insulator spectrometers with integrated GaInAsSb photodiodes for wide-band spectroscopy from 1510 to 2300 nm," *Opt. Exp.*, vol. 21, no. 5, pp. 6101–6108, 2013.
- [12] M. Muneeb, X. Chen, E. M. P. Ryckeboer, A. Malik, G. Mashanovich, and G. Roelkens, "Silicon-on-insulator mid-infrared planar concave grating based (de)multiplexer," in *Proc. IEEE Photon. Conf.*, Bellevue, WA, USA, 2013, pp. 100–101.
- [13] Z. Cheng, X. Chen, C. Y. Wong, K. Xu, and H. K. Tsang, "Mid-infrared suspended membrane waveguide and ring resonator on silicon-on-insulator," *IEEE Photon. J.*, vol. 4, no. 5, pp. 1510–1519, Oct. 2012.
- [14] Y. Xia, C. Qiu, X. Zhang, W. Gao, J. Shu, and Q. Xu, "Suspended Si ring resonator for mid-IR application," *Opt. Lett.*, vol. 38, no. 7, pp. 1122–1124, 2013.
- [15] P. Lin, V. Singh, Y. Cai, L. Kimerling, and A. Agarwal, "Air-clad silicon pedestal structures for broadband mid-infrared microphotonics," *Opt. Lett.*, vol. 38, no. 7, pp. 1031–1033, 2013.
- [16] P. Lin, V. Singh, J. Wang, H. Lin, J. Hu, K. Richardson, J. Musgraves, I. Luzinov, J. Hensley, L. Kimerling, and A. Agarwal, "Si-CMOS compatible materials and devices for mid-IR microphotonics," *Opt. Mater. Exp.*, vol. 3, no. 9, pp. 1474–1487, 2013.
- [17] T. Baehr-Jones, A. Spott, R. Ilic, A. Spott, B. Penkov, W. Asher, and M. Hochberg, "Silicon-on-sapphire integrated waveguides for the mid-infrared," *Opt. Exp.*, vol. 18, no. 12, pp. 12127–12135, 2010.
- [18] Z. Wang, H. Liu, N. Huang, Q. Sun, J. Wen, and X. Li, "Influence of three-photon absorption on mid-infrared cross-phase modulation in silicon-on-sapphire waveguides," *Opt. Exp.*, vol. 21, no. 2, pp. 1840–1848, 2013.
- [19] F. Li, S. Jackson, C. Grillet, E. Magi, D. Hudson, S. Madden, Y. Moghe, C. O'Brien, A. Read, S. Duvall, P. Atanackovic, B. Eggleton, and D. Moss, "Low propagation loss silicon-on-sapphire waveguides for the mid-infrared," *Opt. Exp.*, vol. 19, no. 16, pp. 15212–15220, 2011.
- [20] Z. Cheng, X. Chen, C. Wong, K. Xu, Y. Chen, and H. Tsang, "Mid-Infrared grating couplers for silicon-on-sapphire waveguides," *IEEE Photon. J.*, vol. 4, no. 1, pp. 104–113, Feb. 2012.
- [21] R. Shankar, I. Bulu, and M. Loncar, "Integrated high-quality factor silicon-on-sapphire ring resonators for the mid-infrared," *Appl. Phys. Lett.*, vol. 102, no. 5, p. 051108, 2013.
- [22] S. Khan, J. Chiles, J. Ma, and S. Fathpour, "Silicon-on-nitride waveguides for mid- and near-infrared integrated photonics," *Appl. Phys. Lett.*, vol. 102, p. 121104, 2013.
- [23] P. Lin, V. Singh, L. Kimerling, and A. Agarwal, "Planar silicon nitride mid-infrared devices," *Appl. Phys. Lett.*, vol. 102, no. 25, p. 251121, 2013.
- [24] Y. Chang, V. Paeder, L. Hvozdar, J. M. Hartmann, and H. P. Herzig, "Low-loss germanium strip waveguides on silicon for the mid-infrared," *Opt. Lett.*, vol. 37, no. 4, pp. 2883–2886, 2012.
- [25] A. Malik, M. Muneeb, S. Pathak, Y. Shimura, J. Van Campenhout, R. Loo, and G. Roelkens, "Germanium-on-Silicon Mid-Infrared Arrayed Waveguide Grating Multiplexers," *IEEE Photon. Technol. Lett.*, vol. 25, no. 18, pp. 1805–1808, Sep. 2013.
- [26] A. Malik, M. Muneeb, Y. Shimura, J. Van Campenhout, R. Loo, and G. Roelkens, "Germanium-on-Silicon Planar Concave Grating Wavelength (de)multiplexers in the Mid-Infrared," submitted for publication in *Applied Physics Letters*.
- [27] S. Keyvaninia, M. Muneeb, S. Stankovic, René van Veldhoven, D. Van Thourhout, and G. Roelkens, "Ultra-thin DVS-BCB adhesive bonding of III-V wafers, dies and multiple dies to a patterned silicon-on-insulator substrate," *Opt. Mater. Exp.*, vol. 3, no. 1, pp. 35–46, 2013.
- [28] A. Gassenq, N. Hattasan, E. Ryckeboer, J. B. Rodriguez, L. Cerutti, E. Tournie, and G. Roelkens, "Study of evanescently-coupled and grating-assisted GaInAsSb photodiodes integrated on a silicon photonic chip," *Opt. Exp.*, vol. 20, no. 11, pp. 11665–11672, 2012.
- [29] G. Sun, R. Soref, and H. Cheng, "Design of a Si-based lattice-matched room-temperature GeSn/GeSiSn multi-quantum well mid-infrared laser diode," *Opt. Exp.*, vol. 18, no. 10, pp. 19957–19965, 2010.
- [30] A. Gassenq, F. Gencarelli, J. Van Campenhout, Y. Shimura, R. Loo, G. Narcy, B. Vincent, and G. Roelkens, "GeSn/Ge heterostructure short-wave infrared photodetectors on silicon," *Opt. Exp.*, vol. 20, no. 25, pp. 27297–27303, 2012.
- [31] G. Konstantatos, I. Howard, A. Fischer, S. Hoogland, J. Clifford, E. Klem, L. Levina, and E. Sargent, "Untrassensitive solution-cast quantum dot photodetectors," *Nature*, vol. 442, pp. 180–183, 2006.
- [32] C. Hu, A. Gassenq, Y. Justo, S. Yakunin, W. Heiss, Z. Hens, and G. Roelkens, "Short-wave infrared colloidal quantum dot photodetectors on silicon," in *Proc. 2013 Photon. West Conf.*, San Francisco, CA, USA, 2013, pp. 8631–8679.
- [33] S. Keuleyan, E. Lhuillier, V. Brajuskovic, and P. Guyot-Sionnest, "Mid-infrared HgTe colloidal quantum dot photodetectors," *Nat. Photon.*, vol. 5, pp. 489–493, 2011.
- [34] J. B. Rodriguez, L. Cerutti, P. Grech, and E. Tournie, "Room-temperature operation of a 2.25 μm electrically pumped laser fabricated on a silicon substrate," *Appl. Phys. Lett.*, vol. 94, no. 6, p. 061124, 2009.
- [35] D. Sanchez, L. Cerutti, and E. Tournie, "Single-mode monolithic GaSb vertical-cavity surface-emitting laser," *Opt. Exp.*, vol. 20, no. 14, pp. 15540–15546, 2012.
- [36] A. Bachmann, K. Kashani-Shirazi, S. Arafin, and M.-C. Amann, "GaSb-Based VCSEL with buried tunnel junction for emission around 2.3 μm ,"

- IEEE Select. Top. Quantum, Electron.*, vol. 15, no. 3, pp. 933–940, May/June 2009.
- [37] C. F. R. Mateus, M. Huang, Y. Deng, and C. Chang-Hasnain, “Broad-band mirror using a subwavelength grating,” *IEEE Photon. Technol. Lett.*, vol. 16, no. 7, pp. 1676–1678, Jul. 2004.
- [38] R. Wang, D. Sanchez, and G. Roelkens, “Design of a high contrast grating GaSb-based VCSEL integrated on SOI,” in *Proc. IEEE Photon. Conf.*, 2013, pp. 91–92.
- [39] X. Gai, Y. Yu, B. Kuyken, P. Ma, S. Madden, J. Van Campenhout, P. Verheyen, G. Roelkens, R. Baets, and B. Luther-Davies, “Nonlinear absorption and refraction in crystalline silicon in the mid-infrared,” accepted for publication in *Lasers and Photonics Reviews*.
- [40] B. Kuyken, X. Liu, R. M. Osgood Jr., R. Baets, G. Roelkens, and W. M. J. Green, “Mid-infrared to telecom-band supercontinuum generation in highly nonlinear silicon-on-insulator wire waveguides,” *Opt. Exp.*, vol. 19, no. 21, pp. 20172–20181, 2011.
- [41] S. Uvin, U. Dave, B. Kuyken, S. Selvaraja, F. Leo, and G. Roelkens, “Mid-infrared to telecom-band stable supercontinuum generation in hydrogenated amorphous silicon waveguides,” in *Proc. IEEE Photon. Conf.*, Bellevue, WA, USA, 2013, pp. 380–381.
- [42] B. Kuyken, X. Liu, R. M. Osgood Jr., R. Baets, G. Roelkens, and W. M. J. Green, “A silicon-based widely tunable short-wave infrared optical parametric oscillator,” *Opt. Exp.*, vol. 21, no. 5, pp. 5931–5940, 2013.
- [43] X. Liu, B. Kuyken, G. Roelkens, R. Baets, R. M. Osgood Jr., and W. M. J. Green, “Bridging the mid-infrared-to-telecom gap with silicon nanophotonic spectral translation,” *Nat. Photon.*, vol. 6, pp. 667–671, 2012.
- [44] B. Kuyken, P. Verheyen, P. Tannouri, J. Van Campenhout, R. Baets, W. Green, and G. Roelkens, “Generation of 3.6 μm radiation and telecom-band amplification by four-wave mixing in a silicon waveguide with normal group velocity dispersion,” submitted for publication in *Optics Letters*.
- [45] J. Riemensberger, K. Hartinger, T. Herr, V. Brasch, R. Holzwarth, and T. Kippenberg, “Dispersion engineering of thick high-Q silicon nitride ring-resonators via atomic layer deposition,” *Opt. Exp.*, vol. 20, no. 25, pp. 27661–27669, 2012.
- [46] P. Merritt, R. Tatam, and D. Jackson, “Interferometric chromatic dispersion measurement on short lengths of monomode fiber,” *J. Lightw. Technol.*, vol. 7, p. 703716, 1989.
- [47] J. Hu, “Ultra-sensitive chemical vapor detection using micro-cavity photo-thermal spectroscopy,” *Opt. Exp.*, vol. 18, pp. 22174–22186, 2010.
- [48] E. Holthoff, J. Bender, P. Pellegrino, and A. Fisher, “Quantum cascade laser-based photoacoustic spectroscopy for trace vapor detection and molecular discrimination,” *Sensors*, vol. 10, pp. 1986–2002, 2010.
- [49] X. Wang, Z. Chen, K. Xu, H. Tsang, and J. Xu, “High-responsivity graphene/silicon-heterostructure waveguide photodetectors,” *Nature Photon.*, vol. 7, pp. 888–891, 2013.
- [50] R. Adato and H. Altug, “*In-situ* ultra-sensitive infrared absorption spectroscopy of biomolecule interaction in real time with plasmonic nanoantennas,” *Nature Commun.*, vol. 4, p. 2154, 2013.

Gunther Roelkens received the Graduation degree in electronics engineering (option: microelectronics and optoelectronics) from Ghent University, Ghent, Belgium (with highest honour), in 2002. Since 2002, he has been working in the Photonics Research Group at Ghent University, where he received the Doctoral degree in April 2007, for his work in the field of heterogeneous III–V/Silicon photonics. In this work, the technology for integrating III–V material on top of silicon-on-insulator waveguide circuits was developed and the integration of thin film III–V laser diodes and photodetectors on top of and coupled to the SOI waveguide circuit was demonstrated. Currently, he is working as a tenure track Professor in the same group. His research interests include heterogeneous III–V/silicon integration, efficient fiber-chip coupling, all-optical signal processing, and mid-infrared photonic integrated circuits.

Utsav D. Dave received the Bachelors degree in engineering physics from the Indian Institute of Technology, Guwahati, India, in 2010. Following that, he went on to do the Erasmus Mundus Master of Science in Photonics. He is currently working toward the Ph.D. degree on on-chip nonlinear optics for the mid-infrared regime at Ghent University, Ghent, Belgium.

Alban Gassenq was born in Montpellier in 1983. He received the diploma degree in engineering from the University of Montpellier 2 (UM2), Montpellier, France, in 2006. He received the Ph.D. degree in semiconductors for Mid-IR applications in the laboratory IES from UM2, in 2010. After two years of work in the photonics group INTEC-IMEC on Mid-IR integrated optics, he is currently working as a designer of measurement systems for industrial control in the company Matériau Ingénierie, France.

Nannicha Hattasan received the B.Eng degree in electronics engineering from King Mongkut’s Institute of Technology Ladkrabang, Bangkok, Thailand, and the M.Sc. degree in photonics from the Royal Institute of Technology in Stockholm, Sweden and from the Ghent University, Ghent, Belgium, in 2009. She is currently working toward the Ph.D. degree on heterogeneous integration of III–V and SOI.

Chen Hu received the Masters degree in photonics from the Royal Institute of Technology, Stockholm, Sweden, in 2011. She is currently working toward the Ph.D. degree on mid-infrared photodetectors based on colloidal quantum dots in Photonics Research Group and Physics and Chemistry of Nanostructures Group of Ghent University, Ghent, Belgium.

Bart Kuyken received the B.S. degree in engineering and physics from Ghent University (UGent), Ghent, Belgium, in 2006 and 2008, respectively, the M.Sc. degree in electrical engineering (option: electronic circuits and systems) from Ghent University, and another M.Sc. degree in electrical engineering from Stanford University, Stanford, CA, USA, in 2008 and 2009, respectively. He has been with the Photonics Research Group, UGent, Belgium, on a Doctoral fellowship from the Flemish Research Foundation since 2009 and obtained the Ph.D. degree in 2013.

Francois Leo received the Diploma degree in engineering (physics department) from the University of Brussels, Brussels, Belgium, in 2005. His Masters thesis was entitled: “Microscopic study of $14\text{O} + \text{p}$ elastic scattering”. He then worked towards the Ph.D. degree at the OPERA-photonique Department of the Applied Science Faculty of the Université Libre de Bruxelles, Brussels, Belgium, thanks to a Doctoral fellowship of the Belgian Fund for Scientific Research. He received the Ph.D. degree in applied physical sciences, in November 2010, by defending his thesis entitled “Study of the dissipative structures of passive optical cavities: theory and experiment”. He then stayed one year as a Postdoctoral Researcher in Brussels before joining the Photonics Research Group in Ghent, Belgium.

Aditya Malik received the M.Sc. degree in physics from the Indian Institute of Technology, Delhi, India, in 2010. Currently, he is working towards the Ph.D. degree focused on developing a new waveguide platform for the Mid-IR with the aim to realize a broadly tunable integrated Quantum Cascade Laser.

Muhammad Muneeb was born in 1982 in Pakistan. He received the B.S. degree in electronic engineering from the GIK Institute of Engineering and Technology, Swabi Khabar Pakhtoon Khwa, Pakistan, in 2005, and the Erasmus Mundus Masters degree in photonics from Royal Institute of Technology, Stockholm, Sweden and University of Ghent (UGent), Ghent, Belgium, in 2010. Since November 2010, he is currently working in the Photonics Research Group of INTEC, UGent where his research focus is on III–V/Si photonic circuits for MidIR spectroscopic applications.

Eva Ryckeboer received the Erasmus Mundus Master of Science degree in photonics, in 2009 from Ghent University, Ghent, Belgium; VUB Brussels, Brussels, Belgium; Royal Institute of Technology, Stockholm, Sweden; and the University of Sydney, Sydney, Australia. She then joined the photonics research group at Ghent University, Belgium, where she is currently working toward the Ph.D. degree focusing on integrated spectrometers for *in vivo* glucose monitoring.

Dorian Sanchez received the Ph.D. degree from University of Science, Montpellier, France, in 2012, for his work on a new-confinement method for GaSb-based vertical-cavity surface-emitting lasers (VCSELs). Since 2013, he is holding a Postdoctoral position in the Photonics Research Group, Ghent University, Ghent, Belgium. He is currently working on the integration of GaSb-based VCSELs on SOI using High Contrast Grating mirrors. His current research interests include design and fabrication of GaSb-based VCSELs and Silicon photonics.

Sarah Uvin received the Bachelors degree in electrical engineering and her Master of Science degree in photonics at Ghent University, Ghent, Belgium, in 2011 and 2013, respectively. She is now working towards the Ph.D. degree in the Photonics Research Group of Ghent University.

Ruijun Wang received the B.Sc. degree from Xidian University, Shaanxi, China, in 2009, and the M.Sc. degree from Shandong University, Shandong, in 2012. He is currently working toward the Ph.D. degree at Photonics Research Group, Ghent University, Ghent, Belgium. His current research interests include III–V/silicon integration and mid-infrared photonics.

Zeger Hens is currently a Professor at Ghent University, Ghent, Belgium. He is heading the Physics and Chemistry of Nanostructures group dealing with the synthesis and optical/electrical properties of colloidal nanoparticles.

Roel Baets is currently a Full Professor at Ghent University (UGent), Ghent, Belgium. He is also associated with IMEC, Leuven, Belgium. He has management responsibilities within the Photonics Research Group of UGent, the Center for Nano- and Biophotonics (NB Photonics) of UGent, the international Erasmus Mundus M.Sc. program in Photonics and the joint UGent–IMEC research program on silicon photonics.

Yosuke Shimura received the Masters degree of engineering, in 2009, and the Ph.D. degree, in 2011, both from Nagoya University, Nagoya, Japan. In June 2012, he joined IMEC in Leuven, Belgium. From October 2012 till present, he is receiving a fellowship from FWO, Belgium.

Federica Gencarelli received the bachelors and masters degrees in electronic engineering, in 2009, from the University of Calabria, Calabria, Italy, both of which were awarded with distinction. In 2010, she joined the EPI group at IMEC, where she is currently working toward the Ph.D. degree on the epitaxial growth and material characterization of GeSn alloys, in connection with the MTM Department of the Katholieke Universiteit Leuven, Leuven, Belgium.

Benjamin Vincent received the M.Sc. and Ph.D. degrees from Grenoble Institute of Technology, Grenoble, France, in 2005 and 2008, respectively. He worked on Germanium On Insulator (GeOI) substrate fabrication in CEA–LETI (France) during his thesis. From 2008 to 2012, he worked on group IV epitaxial growth for advanced CMOS technology at IMEC (Belgium). He then joined the Intel Corp., CA, USA, in 2013.

Roger Loo received the Masters degree in experimental physics, in 1993, and the Ph.D. degree, in 1997, both from the R.W.T.H. Aachen, Aachen, Germany. From December 1993 to November 1996, he received a fellowship from SIEMENS A.G. in Munich, Germany. In January 1997, he joined IMEC in Leuven, Belgium. Dr. Loo has (co-) authored more than 210 papers (listed in INSPEC database) about Group IV and III/V epitaxy and related topics.

Joris Van Campenhout received the Masters degree in physics engineering, in 2002, and the Ph.D. degree in electrical engineering, in 2007, both from Ghent University, Ghent, Belgium. After his Ph.D., he worked as a Postdoctoral researcher at the IBM TJ Watson Research Center in New York, NY, USA. In 2010, he started at IMEC, Belgium, where he currently is the Program Manager Optical I/O.

Laurent Cerutti was born in 1976. Since 2006, he is currently an Associate Professor at the University of Montpellier 2, Montpellier, France, where his research is focused on the growth of antimonide based semiconductor by molecular beam epitaxy for MIR photonics.

Jean-Baptiste Rodriguez is 35 years old. He received the Ph.D. from the University of Montpellier, Montpellier, France, in 2005, and then joined the Center for High Technology Materials (Albuquerque, NM, USA) for a two year Postdoctorate. He is currently the Chargé de Recherche at CNRS (CR1). He has about ten years of experience in the T2 SL technology and the study of new epitaxial techniques by MBE, such as the epitaxy of antimonide-based materials on silicon substrates for integrated photonics.

Eric Tournié received the Ph.D. degree from the University of Montpellier (UM2), Montpellier, France, in 1990. From 1990 to 1993, he was a Staff Member of the Max-Planck-Institute in Stuttgart, Germany, working on InAs-based highly-strained heterostructures on InP and GaAs substrates. In 1993, he joined CRHEA/CNRS, Valbonne, France, to work on ZnSe-based heterostructures for blue–green lasers. In 1999, he initiated a program on GaInNAs heterostructures and devices for telecom and solar-cells applications. In 2002, he became Professor of electrical engineering at the UM2, France, where he is currently the Head of the III–Sb group. He is also a Senior Member of the Institut Universitaire de France (IUF), France. He coordinated the GINA1.5 FET-IST (FP5), DOMINO (FP6, 2005–2008), and MIRNANO (ANR PNANO 2008) projects. He has been the Principal Investigator for UM2 in the NEMIS (FP6, 2006–2009) and TRAIN2 (FEDER SUDOE 2011–12) projects. He is the Coordinator of OPTOSi (Blanc 2012) project and of the EXTRA EquipEx. He is a Member of the Program Committee and/or Int. Advisory Committee of the Int. Conf. on Mid-Infrared Optoelectronics: Materials and Devices, Int. MBE conference, Int. Symposium on Compounds Semiconductors, Euro-MBE series. He serves regularly as an expert for French programs as well as for the EPSRC (U.K.) and for the IST priority of FP6 and FP7, and as a Referee for several scientific journals. He is a Member of the Editorial Board of J of Physics D: Applied Physics. Dr. Tournié is author/co-author of upto 190 papers in refereed journals and contributed upto 100 communications in international conferences.

Xia Chen received the B.Eng. and Ph.D. degrees in electronics engineering from The Chinese University of Hong Kong, Hong Kong, in 2006 and 2010, respectively. He is currently a Royal Society Newton Fellow at Optoelectronics Research Centre, University of Southampton, Southampton, U.K., working on silicon photonics. He has authored and coauthored over 50 papers in technical journals and international conferences.

Milos Nedeljkovic is currently working towards the Ph.D. degree at the University of Southampton, Southampton, U.K.. His research interests include photonic components and modulation mechanisms in Group-IV materials for mid-infrared wavelengths.

Goran Mashanovich received the Dipl. Ing. and the M.Sc. degrees in optoelectronics from the University of Belgrade, Belgrade, Serbia, and the Ph.D. degree in silicon photonics from the University of Surrey, Surrey, U.K.. He is currently a Royal Society Research Fellow and Reader in Silicon Photonics at the Optoelectronics Research Centre, University of Southampton, Southampton, U.K.

Li Shen received the B.Sc. and M.Phil. degrees from Huazhong University of Science and Technology, Wuhan, China, in 2009 and 2012, respectively. Following this, he joined the ORC at the University of Southampton, Southampton, U.K., where he is currently working towards the Ph.D. degree in the area of novel semiconductor photonic devices.

Noel Healy received the B.Sc. degree in materials science from the Faculty of Engineering, University of Limerick, Limerick, Ireland, in 2002, and followed this with the Ph.D. degree in fiber optics from the same institution in 2007. In 2004, Noel took a research position at the Lightwave Technology Research Centre at the University of Limerick, where he developed some of his early Ph.D. work on tapered and polished fiber devices to a commercial device level. He joined the Photonic, Electronic and Plasmonic Microstructured Optical Fiber group at the Optoelectronics Research Centre, University of Southampton, Southampton, U.K., in 2008. His current research focuses on the development of novel semiconductor optical fibers and waveguides and their implementation as functional optical devices.

Anna C. Peacock received the Ph.D. degree from Optoelectronics Research Centre, University of Southampton, Southampton, U.K., in 2004. Following a five year Royal Academy of Engineering Research fellowship, she was appointed to the position of Reader and is currently working in the area of semiconductor nonlinear photonics.

Xiaoping Liu received the B.S. degree from Nanjing University, Nanjing, China, in 2003, and the Ph.D. degree in electrical Engineering from Columbia University, New York, NY, USA, in 2011. He is currently a Professor at Nanjing University with research interests in nano-photonics devices and novel fiber optic devices.

Richard Osgood (F'87) received the Ph.D. degree in physics from Massachusetts Institute of Technology, Cambridge, MA, USA, in 1973. He is currently a Higgins Professor of Electrical Engineering and Applied Physics and Applied Mathematics at Columbia University, New York, NY, USA, and Director of the Laboratory on Light/Surface Interactions. He is a recipient of the R.W. Wood Award of the OSA and is a Fellow of the APS, and the OSA.

William M. J. Green (M'03–SM'13) received the Ph.D. degree in electrical engineering from the California Institute of Technology, Pasadena, CA, USA, in 2005. Dr. William Green is currently a Research Staff Member at the IBM Thomas J. Watson Research Center, Yorktown Heights, NY, USA, where his research activities encompass the design of optical devices and integrated systems for terabit-per-second-class silicon nanophotonic interconnects. In addition, Dr. Green's work has extended the silicon photonic integrated circuit platform to the generation and processing of mid-infrared optical signals, for various applications in molecular spectroscopy, environmental sensing, and medical diagnostics.